

Mycoflora Associated with Some Textiles in Jeddah City

Saleh M. Al-Garni, Saleh Kabli,
Fatimah Al-Shehrei and Zakiah Al-Ganawi

*Biological Sciences Department, Faculty of Science,
King Abdulaziz, University, Saudi Arabia*

Abstract. The Mycoflora of eight different fabrics (natural, synthetic, and blended), collected from warehouses in Jeddah, Saudi Arabia, were isolated by different methods; contact plate, dilution, Stomacher, and moisturization that followed by contact plate method. Twenty three different species were isolated. Aspergilli were the most dominant (35%), followed by penicilli and fusaria (13% each). The highest fungal count (1932 CFU/cm²) was concomitant with cotton fabrics, even when blended with polyester. Wool textiles came in the second order of fungal counts (1421 CFU/cm²). While natural silk fibers, was less susceptible for fungal attack, polyamide textiles had moderate affinity toward fungal colonization.

The influence of some environmental conditions (temperature, growth medium, pH and relative humidity) on the linear growth of 10 representative isolates, that may have health hazards to man (*Alternaria alternata*, *Aspergillus flavus*, *A. fumigatus*, *A. niger*, *Fusarium oxysporum*, *Geotrichum* sp., *Gliocladium atrum*, *Penicillium chrysogenum*, *Rhizopus nigricans* and *Trichoderma viride*), were tested. The cellulytic and proteolytic activities of these fungi indicated that *T. viride*, *Geotrichum* sp. *A. niger*, *A. alternata* and *P. chrysogenum* were with the highest activities. Antimycotic activity of two detergents was studied and indicated that the tested fungi responded differently to the detergent type and its concentration.

Introduction

The importance of textile fibers has changed over the years and moreover differs according to culture^[1]. In Europe and North America, by 1900, cotton provided about 80% and the rest was wool, flax and silk. Since that time, man-made fibers have been developed and increased in importance^[2]. So, the

degradation of cellulosic textiles and the prevention of biogenous decay have changed. The use of man-made fiber textiles in the place of natural fibers does not automatically mean that they are "biologically resistant"^[3]. Many synthetic fabrics may be easily attacked and decomposed by microorganisms^[4].

Fabrics are suitable environments for the growth and multiplication of microorganisms. Many investigations were made on mycoflora found on textiles exposed to indoors and outdoors. It has been shown that microbial population in air "aeromycoflora" is similar to that communities of the organisms found in soil^[5-10].

Aeromycoflora are biopollutants and have important impacts on medicine. They cause various health hazards in man and other organisms; they cause a variety of mycoses and allergies^[11-13].

Mycoflora have the priority within the microorganisms that attack fabrics and hydrolyze their components by their hydrolyzing enzymes as cellulases and proteases, especially under favorable conditions of temperature, humidity and pH^[14].

In Saudi Arabia there are poor records on the mycoflora of different types of fabrics^[15]. So the present work aimed to characterize the mycoflora associated with some natural, synthetic and blended fibers and to study the effect of some environmental conditions on the isolated fungi, as well as their cellulytic and proteolytic activities.

Materials and Methods

Two hundred samples of natural fibers (cotton, lenin, silk and wool textiles), synthetic fibers (nylon of polyester and polyester of polyamide textiles), and blended textiles (75% cotton with 25% polyester and 65% cotton with 35% polyester), were collected from warehouses at Jeddah, Saudi Arabia (twenty five samples of each textile). The samples were collected in sterile plastic bags and stored at 4°C till analysis.

Moisture Content

Twelve grams of each sample were used to determine the moisture content at 100°C, until constant weight. The percentages of moisture contents were 4.3, 3.5, 0.25, 5.25, 0.5, 0.75, 2.7 and 2.5 for cotton, lenin, silk, wool, nylon, polyester, cotton with polyester (75 with 25%) and cotton with polyester (65 with 35%), respectively.

Estimation of Textile Associated Fungi

Five different methods were used to isolate the textiles mycoflora using potato dextrose agar (PDA) medium, to which penicillin and streptomycin were added to prevent bacterial growth^[16-20]. These methods were:

1 – Contact Plate

Petri-dishes with PDA medium were used. They were pressed onto the fabric test samples (1 cm²) and then incubated at 28°C for 2 weeks. There after, the number of colonies was counted.

2 – Dilution

Pieces of tested fabrics (1 cm² each) were mixed thoroughly with 10 ml sterile distilled water in 50 ml conical flasks, shaken at 250 rpm for 20 min. One ml was used to inoculate Petri-dish containing PDA medium, then incubated for 2 weeks at 28°C. Colony counts were then carried out.

3 – Stomacher

A fabric test sample (100 cm²) was placed in a sterile polyurethane bag with 100 ml 0.9% NaCl. The bag was sealed and run for 3 min in a stomacher 400®. One ml fluid was spread onto PDA plates which then incubated at 28°C for 2 weeks.

4 – Moisturization

Ten pieces (1 cm², each) were moistening with sterile distilled water in empty Petri-dish, incubated at 28°C for six months. Moistening was carried out weekly.

5 – Contact Plate Method for Moisturized Fabrics

Petri-dishes containing PDA were pressed onto the fabric sample of the last method (moisturization) and then incubated at 28°C for 2 weeks. The number of colonies was then counted. The isolated fungi by the above five methods are maintained on PDA slants at 5°C with monthly intervals subculture.

Identification of the Isolated Fungi

The developing fungi, by the five used isolation methods, were purified and identified. Identification was based on macro and microscopic characters^[21-27]. The fungal counts were the sum of the used five isolation methods.

Environmental Studies

The effect of some cultural conditions as, incubation temperature, nutrient media, pH value and relative humidity on the linear growth of selected representative 10 isolates that may have health hazards in man (*Alternaria alternata*, *Aspergillus flavus*, *A. fumigatus*, *A. niger*, *Fusarium oxysporum*, *Geotrichum* sp., *Gliocladium atrum*, *Penicillium chrysogenum*, *Rhizopus nigricans* and *Trichoderma viride*), was carried out. The inoculum was in the form of disks, prepared using a sterile cork poorer (5mm in diameter). The disks were obtained from homogenous growth of 4 days old cultures grown on PDA medium at $28^{\circ} \pm 2^{\circ}$. Each treatment was carried out in 5 replica and the estimated results were the arithmetic mean.

Effect of Growth Temperature

The linear growth (cm) of the tested moulds on PDA medium was estimated at incubation temperatures ranging from 10-55°C for 14 days.

Effect of Different Nutrient Media

The tested moulds were cultivated on five different media of Difco (PDA, Malt Extract, Czapek's, Rose Bengal agar and Sabouraud) and the linear growth was estimated regularly for 24 days of incubation or until the completion of growth in Petri-dishes.

Effect of Initial pH Value

The influence of different pH values (4-12) on the linear growth of the test fungi on PDA medium, after 14 days of incubation at $28^{\circ} \pm 2^{\circ}$ C, was estimated.

Influence of Relative Humidity (R.H)

Levels of R.H (14.5 – 100%) were maintained using different amounts of KOH and NaOH^[28]. The test mould was inoculated to PDA, then the Petri-dish upside down, where the tested R.H (5ml) was placed in the lid. Incubation for 14 days at $28^{\circ} \pm 2^{\circ}$ C, there after the linear growth was recorded.

Antimicrobial Activity of Detergents

Two different detergents (Tide and Ariel of Procter and Gamble) were tested for their antifungal activity. Three different levels were used (4,8 [recommended level] and 16 g/l) The tested detergent level was mixed aseptically with PDA (at 50°C) poured in sterile Petri-dishes and after solidification inoculated with the tested fungal growth (disks), incubation for 14 days at $28^{\circ} \pm 2^{\circ}$ C, where the linear growth was estimated.

Enzymatic Activity

The cellulytic and proteolytic activities of the selected 10 isolates were estimated.

Cellulytic Activity

Aliquots (100ml) of cellulases promoting medium^[29], at pH4, were dispensed in 250ml Erlmeyer flasks, inoculated with 1 ml spore suspension (10^6 spore/ml) of 5 days old culture and incubated for 12 days at 2°C. The crude enzyme (filtrate) was isolated by centrifugation at 3000 rpm for 20 min and the enzyme activity was determined, using CMC substrate^[30,31], as μmol glucose/h/ml crude enzyme. The produced glucose was estimated colorimetrically using dinitrosalicylic acid^[32-34].

Proteolytic Activity

The proteases of the tested fungi were estimated using modified Czapek's medium of the following composition (g/l): maltose, 20; casien, 4; K_2HPO_4 , 1; KCl, 0.5; ferric chloride 0.005. The enzyme activity was determined in the filtrate and the enzyme units were calculated using tyrosine standard^[32-34], as follows:

$$\text{Enzyme units} = \frac{\mu\text{g tyrosine} \times \text{crude enzyme dilution}}{\text{Time of enzyme incubation (min)}}$$

Three replica at least of each treatment were carried out and the recorded results are the arithmetic mean.

Results and Discussion

Mycoflora of Different Textiles

Twenty three different fungal species were isolated from the tested fabrics (Table 1). Aspergilli represent about 35%, penicilli and fusaria were about 13% of each and the rest species were represented by only one species (4.4%). It was reported that aspergilli, penicilli and fusaria were the most dominant moulds in textiles^[15]. The cellulosic textiles of cotton represent the highest fungal counts 1932 CFU/cm², *i.e.*, cotton fibers represent a prime substance for microbial attack and/or cotton fibers were more contaminated during the different stages of cotton processing, since in fields up to the form of textile. Even cotton in its blended form with polyester resulted in about 3.8, 2.4 fold increase of fungal count when mixed with 75, 65%, respectively, as compared with synthetic textiles of polyester only. Wool, as a natural fiber, was in the second order from the stand point of fungal count, while silk textiles were the less susceptible natural fibers for fungal attack. It is noteworthy that the polyamide textiles have

Table 1. Total count (CFU/cm²) of fungi isolated from 8 different fabrics (25 sample of each), with 5 different laboratory methods after 14 days of incubation at 28°C using PDA medium.

Fungus	Cotton		Lenin		Silk		Wool		Nylon		Polyester		Blended cotton (75%) Polyester (25%)		Blended cotton (65%) Polyester (35%)		
	Total	Freq.*	Total	Freq.*	Total	Freq.*	Total	Freq.*	Total	Freq.*	Total	Freq.*	Total	Freq.*	Total	Freq.*	
<i>Alternaria alternata</i>	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Aspergillus	1204	25	574	25	307	19	631	23	247	12	100	8	622	16	409	14	
<i>A. flavus</i>	94	5	33	2	58	3	111	6	-	-	-	-	61	4	166	6	
<i>A. fumigatus</i>	250	4	187	5	40	6	274	8	-	-	-	-	144	4	100	3	
<i>A. humicola</i>	-	-	40	7	-	-	-	-	-	-	-	-	-	-	-	-	-
<i>A. niger</i>	410	9	201	8	62	5	148	7	71	4	30	3	183	3	143	5	
<i>A. terreus</i>	50	4	78	1	130	2	-	-	14	1	-	-	-	-	-	-	
<i>A. ustus</i>	190	2	20	1	3	1	31	1	82	2	53	2	74	2	-	-	
<i>A. versicolor</i>	210	1	15	1	14	2	67	1	80	5	17	3	160	3	-	-	
Fusarium	84	7	-	-	-	-	71	2	280	3	-	-	-	-	30	1	
<i>F. dimerum</i>	54	3	-	-	-	71	2	-	-	-	-	-	-	-	-	-	
<i>F. oxysporum</i>	-	-	-	-	-	-	-	-	170	2	-	-	-	-	30	1	
<i>F. poae</i>	30	4	-	-	-	-	-	-	110	1	-	-	-	-	-	-	
<i>Geotrichum</i> sp.	-	-	-	-	-	-	-	-	-	-	-	-	138	2	-	-	
<i>Gliocladium atrum</i>	-	-	-	-	-	-	-	-	27	5	-	-	-	-	41	3	
<i>Mucor mucedo</i>	22	3	11	2	40	2	137	6	19	2	-	-	38	2	61	3	

Table 1. Contd.

Fungus	Cotton		Lenin		Silk		Wool		Nylon		Polyester		Blended cotton (75%) Polyester (25%)		Blended cotton (65%) Polyester (35%)	
	Total	Freq.*	Total	Freq.*	Total	Freq.*	Total	Freq.*	Total	Freq.*	Total	Freq.*	Total	Freq.*	Total	Freq.*
Penicillium	372	9	190	5	140	3	255	15	203	4	178	6	380	6	166	7
<i>P. chrysogenum</i>	340	6	180	4	140	3	215	9	203	4	148	4	380	6	166	7
<i>P. janczewskii</i>	20	1	-	-	-	-	33	5	-	-	-	-	-	-	-	-
<i>Penicillium</i> sp.	12	2	10	1	-	-	7	1	-	-	30	2	-	-	-	-
Rhizoctonia	120	4	50	3	11	1	84	9	119	5	162	4	-	-	-	-
<i>Rhizoctonia solani</i>	120	4	50	3	11	1	13	2	119	5	-	-	-	-	-	-
<i>Rhizoctonia</i> sp.	-	-	-	-	-	-	71	1	-	-	162	4	-	-	-	-
<i>Rhizopus nigricans</i>	70	4	-	-	-	-	312	5	-	-	-	-	110	3	109	8
<i>Sporothlycladim xysogenum</i>	-	-	-	-	-	-	-	-	-	-	-	-	130	2	14	1
<i>Sporotrichum laxum</i>	-	-	-	-	-	-	-	-	40	2	-	-	70	3	-	-
<i>Trichoderma viride</i>	60	5	12	1	-	-	-	-	-	-	-	-	-	-	130	2
Total	1932	57	837	36	498	25	1421	54	935	31	400	18	1514	37	979	37

$$*Frequency = \frac{\text{Times of fungus isolation}}{\text{Number of fabric samples (25)}} \times 100$$

moderate affinity toward mycoflora attack as compared to natural, synthetic and blended textiles. It was reported that the high fungal counts in textiles usually due to polluted storage places, transportation, and handling of textiles [36,37]. The last factors beside the hot humid atmosphere of Jeddah city, almost all over the year, encourage fungal attack, growth and multiplication.

The results revealed the presence of some isolates as *Aspergillus fumigatus*, *A. niger*, *A. flavus*, *A. terreus*, *Fusarium* sp., *Geotrichum* sp. and *Mucor* sp. that cause various health hazards to human being such as allergies, respiratory diseases and cutaneous diseases when in contact with human body during cloth wearing, as well as formation of mycotoxins [38-40].

The count and identification data showed variations in both fungal genera and species, this finding was reported by several workers [8,40,41].

Environmental Studies

Effect of Growth Temperature

The results (Fig. 1) indicated that each fungus has an optimum growth temperature and needs a certain range of temperature to attain detectable growth values. Seven moulds namely; *Alternaria alternata*, *Aspergillus flavus*, *A. niger*, *Fusarium oxysporum*, *Rhizopus nigricans*, *Geotrichum* sp. and *Trichoderma viride* attain their optimum linear growth at 25°C, while *A. fumigatus*, *Gliocladium atrum* and *Penicillium chrysogenum* accept their optimum growth at 35°C. However, the tested fungi failed to grow at 10 and 55°C. These results indicated that the tested fungi are considered to be mesophilic [42-44].

Effect of Different Growth Media

The results (Table 2) indicated that under the tested conditions the nutritional requirements of the tested fungi were not dependent on the genus of the fungus, but on the mould species. Whereas, potato dextrose agar (PDA) medium provided nutrient quality and/or quantity that were optimum for the linear growth of *Alternaria alternata*, *Aspergillus fumigatus*, *Geotrichum* sp., *Rhizopus nigricans* and *Trichoderma viride*, rose bengal medium provided ingredients in harmony with the least growth of *A. alternata*, *A. flavus*, *Fusarium oxysporum* and *Penicillium chrysogenum*. While, *A. flavus* and *A. niger* gave the highest growth on sabouraud and malt extract media. The ingredients of PDA and rose bengal media were not in harmony to their growth. On the other hand, PDA and sabouraud media stimulated the highest growth of *P. chrysogenum*. However, malt medium was the most adequate for *G. atrum* growth. These findings reflect the varied affinity of the tested fungi to utilize monomer, oligomeric and polymeric sugars, as well as nitrogenous materials and other ingredients of media [45]. According to

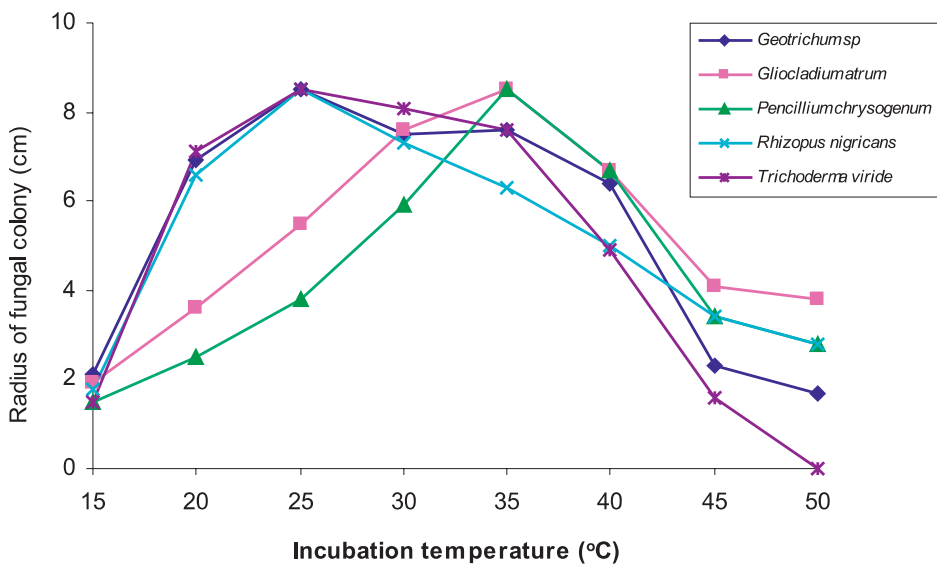
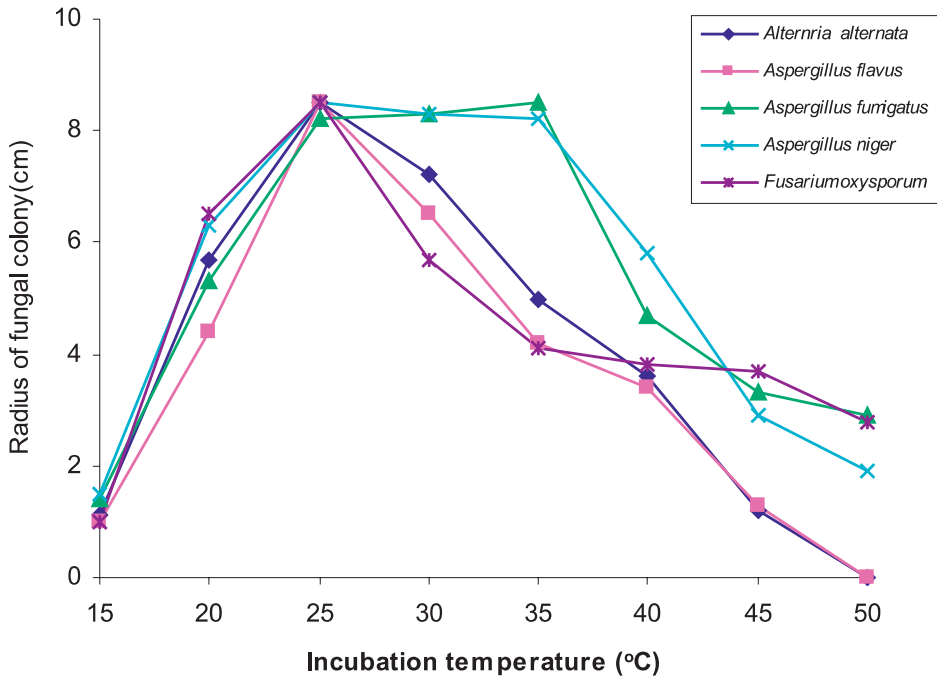


Fig. 1. Effect of incubation temperature on the linear growth (cm) of the tested fungi.

Table 2. Effect of different growth media on the linear growth (cm) of the tested fungi for 24 days of incubation.

Fungus	Growth medium	Incubation period (day)											
		2	4	6	8	10	12	14	16	18	20	22	24
<i>Alternaria alternata</i>	Czapek's	1.5	2.5	3.8	4.5	6.3	7.5	8.5*					
	Malt	2	3.5	4.9	5.7	6.7	8.5*						
	PDA	2.1	4.5	8.5*									
	Rose-Bengal	1.5	2.4	3.3	4.1	4.9	5.5	6.1	6.9**				
	Sabouraud	1.9	2.3	4.5	6.8	7.5	8.5*						
<i>Aspergillus flavus</i>	Czapek's	2.3	4.4	5.8	6.8	7.5	8.5*						
	Malt	2.5	5.1	8.5*									
	PDA	2.1	4.7	6.3	7.5	8.5*							
	Rose-bengal	1.5	2.3	3.8	4.7	5.6	6.7	7.1	8.5*				
	Sabouraud	4.7	6.3	8.5*									
<i>Aspergillus fumigatus</i>	Czapek's	3.7	4.8	6.7	7.5	8.5*							
	Malt	3.5	6.1	7.5	8.5*								
	PDA	4.5	8.5*										
	Rose-Bengal	3.5	4.5	5.9	7.8	8.5*							
	Sabouraud	4.7	6.9	8.5*									
<i>Aspergillus niger</i>	Czapek's	2.5	5.3	7.3	8.5*								
	Malt	2.5	6.6	8.5*									
	PDA	2.6	4.5	5.7	6.3	7.1	8.5*						
	Rose-bengal	2	3.7	4.3	5.6	7.3	8.5*						
	Sabouraud	3.2	5.8	8.5*									
<i>Fusarium oxysporum</i>	Czapek's	2.5	4.3	5.3	6.4	7.8	8.5*						
	Malt	2.5	4.5	6.3	7.2	8.5*							
	PDA	2.3	4.4	5.7	7	8.5*							
	Rose-Bengal	1.5	2.6	3.1	4.4	5.2	6	6.7	7.2	7.8**			
	Sabouraud	2.9	5.5	8.5*									
<i>Geotricum sp.</i>	Czapek's	6.5	7.5	8.5*									
	Malt	5.5	7.5	8.5*									
	PDA	7.3	8.5*										
	Rose-bengal	5.7	7.5	8.5*									
	Sabouraud	6.5	7.8	8.5*									
<i>Gliocladium atrum</i>	Czapek's	2.5	4.7	5.3	6.2	7.7	8.5*						
	Malt	2.5	6.1	8.5*	6.2	7.7	8.5*						
	PDA	3.5	5.9	7.1	8.5*								
	Rose-Bengal	2.1	4.3	6.8	7.1	8.5*							
	Sabouraud	2.3	4.8	6.3	7.2	8.5*							
<i>Panicillium chrysogenum</i>	Czapek's	2.1	3.2	4.5	5.7	6.8	7.1	8.5*					
	Malt	2	3.8	4.7	5.3	6.4	7.5	8.5*					
	PDA	2.5	5.3	6.5	7.5	8.5*							
	Rose-Bengal	1.2	2	2.5	2.9	3.1	3.8	4.3	4.9	5	5.8	6.1	6.7**
	Sabouraud	2.3	4.6	5.7	7.1	8.5*							

Table 2. Contd.

Fungus	Growth medium	Incubation period (day)											
		2	4	6	8	10	12	14	16	18	20	22	24
<i>Rhizopus nigricans</i>	Czapek's	6.1	7.9	8.5*									
	Malt	5.5	7.5	8.5*									
	PDA	6.5	8.5*										
	Rose-bengal	5.2	7.8	8.5*									
	Sabouraud	4.7	7.6	8.5*									
<i>Trichoderma viride</i>	Czapek's	5.5	7.4	8.5*									
	Malt	5.8	7.4	8.5*									
	PDA	6.2	8.5*										
	Rose-Bengal	4.5	7	8.5*									
	Sabouraud	4.9	7.1	8.5*									

*The growth completed in the Petri-dish.

**The growth ceased in the Petri-dish.

the time required for each fungus to attain its highest linear growth on the tested medium, two groups can be generally recognized. First: fast growing moulds that attain their growth within 2-6 days of incubation (*Geotrichum* sp., *R. nigricans* and *T. viride*). Second: moderate growing fungi, which reached their highest growth within 8-16 days, these included the rest tested fungi. However, the maximum growth of both *F. oxysporum* and *P. chrysogenum* on rose bengal medium was attained after 18 and 24 days of incubation, respectively.

Effect of pH Value

The growth of the tested fungi (Fig. 2) responded differently to the hydrogen ion concentration of PDA. They can grow satisfactory at pH values: 4-9, and higher pH resulted in lower growth values. *A. flavus*, *A. niger* and *G. atrum* can grow up to pH 12, while the rest fungi failed to grow under these conditions. However, *F. oxysporum*, *Geotrichum* sp. and *P. chrysogenum* aborted at pH11. PDA of pH6 was optimal for the highest linear growth values of the tested fungi, except aspergilli that attain, the highest growth at pH 7. The influence of pH values on the fungal growth was reported by many workers^[42,46].

Influence of Relative Humidity (R.H)

The linear growth of test fungi was influenced differently under the tested R.H (Fig. 3). The growth of *A. fumigatus*, *A. niger*, *Geotrichum* sp., *R. nigricans* and *T. viride* increased regularly with R.H increasing up to 100%. The same figure was reached for *F. oxysporum*, *G. atrum*, and *P. chrysogenum* but at 95% R.H. However, *A. alternate* and *A. flavus* can grow satisfactory at lower humidity (85%). It was reported that moulds that have the ability to hydrolyze

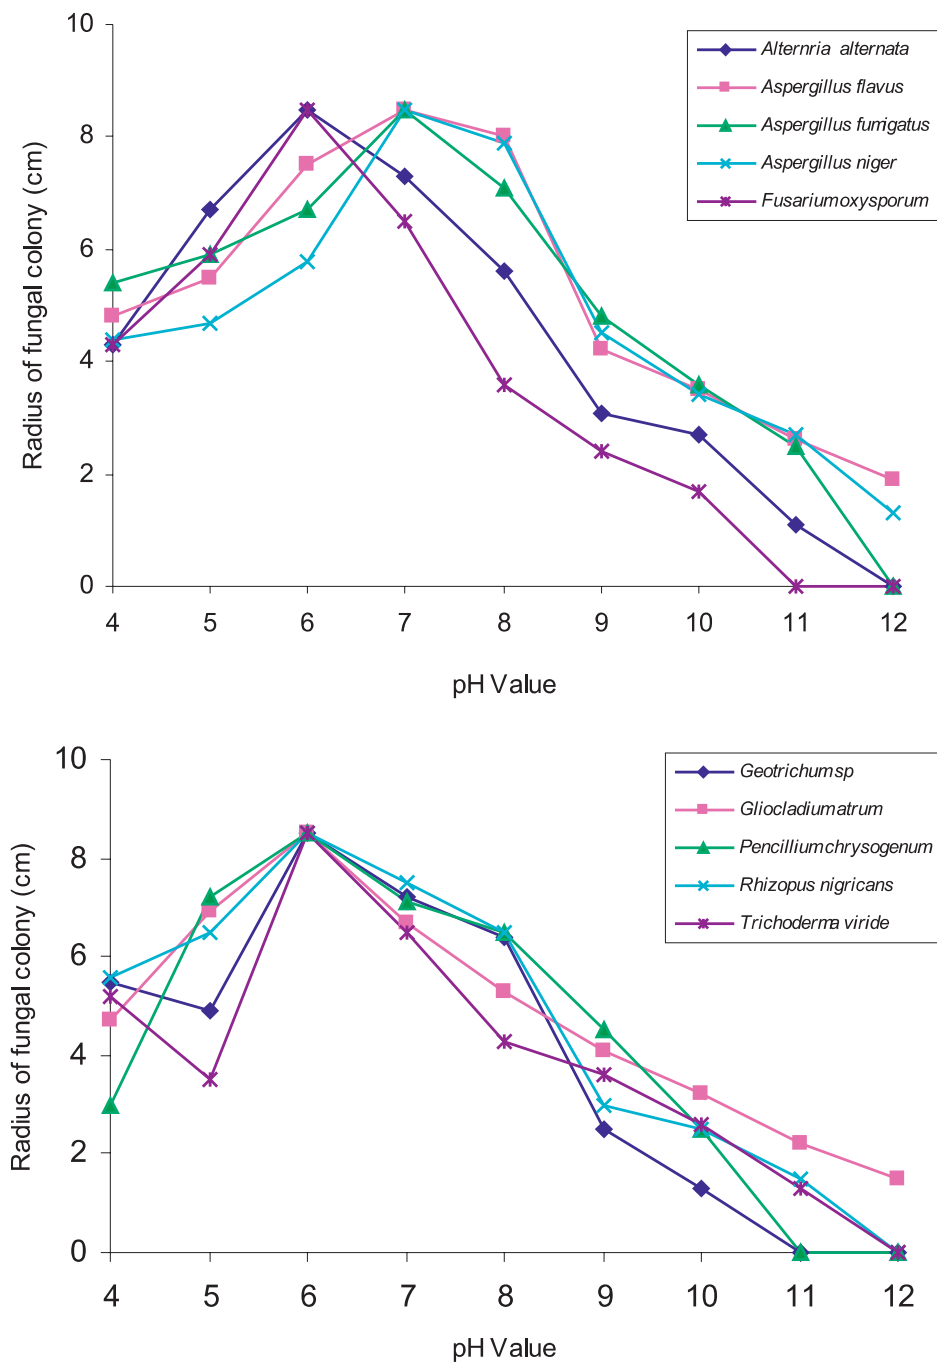


Fig. 2. Effect of different pH values on the linear growth (cm) of the tested fungi.

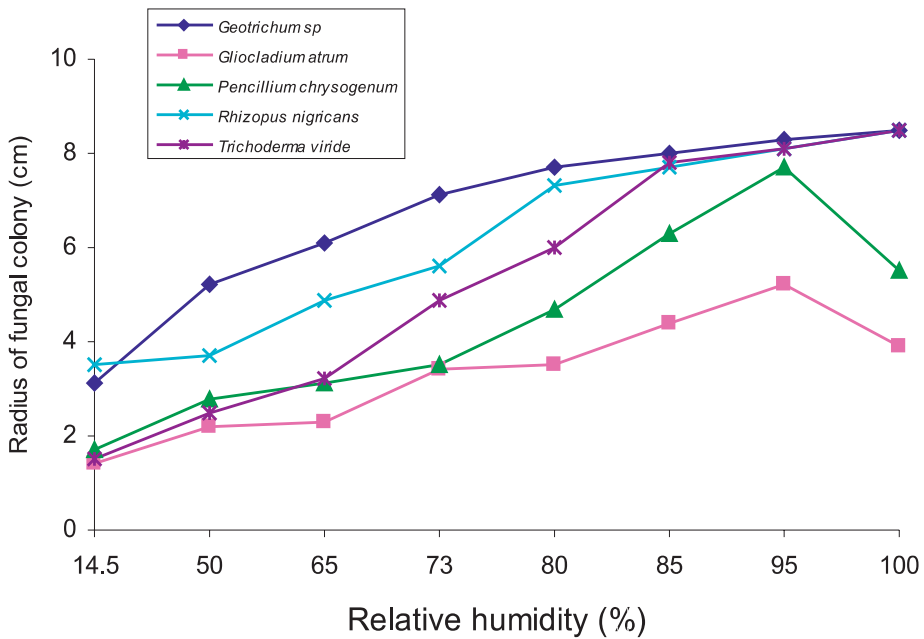
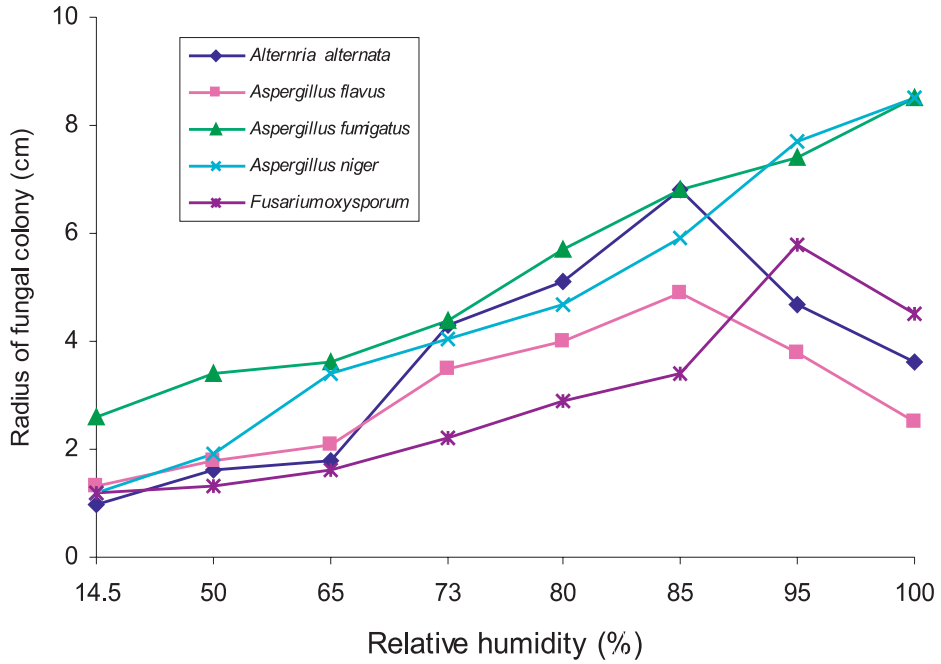


Fig. 3. Effect of different relative humidities on the linear growth (cm) of the tested fungi.

natural materials such as wood, textiles and papers stimulated at R.H more than 75% and their hydrolyzing activities increased with R.H increasing^[47,48].

Enzymatic Activity

The previous study indicated that the tested environmental conditions (incubation temperature, pH and R.H) had great influence on the growth of the isolated fabrics mycoflora. In order to study how many of these fabrics can stand out the deterioration risk that can be attained by their mycoflora, the cellulytic and proteolytic activities were studied.

Cellulytic Activities

The data indicated that of the tested fungi (Fig. 4), *T. viride* has the priority to produce cellulases (0.387 μmol glucose /h/ml crude enzyme) followed by *Geotrichum* sp. and *A. niger* (0.354 and 0.321 μmol glucose /h/m, respectively). While, *R. nigricans*, *A. alternata* and *P.chrysogenum* were with lower activities (0.25 and 0.3 μmol glucose /h/ml). However, the rest fungi showed the least cellulytic activities (less than 0.25 μmol glucose /h/ml). The cellulytic activities of different fungi were reported by many workers^[49,54].

Proteolytic Activities

The results (Fig. 5) revealed that *T. viride* has the highest proteolytic activities (58.6 En.U.). While *A. alternata*, *Geotrichum* sp., *A. niger* and *P. chrysogenum* were with moderate activities (37.6 – 43 En.U.). However, the rest of the tested fungi showed lower activities (less than 25 En.U.). The proteolytic activities of fungi were reported by^[55-59].

The cellulytic and proteolytic activities showed that *T. viride*, *Geotrichum* sp., *A. niger*, *A. alternata* and *P.chrysogenum* (in descending order) have higher activities of both cellulases and proteases, so the risk of fabrics (natural, synthetic and blended) deterioration by them is highly expected when they present as textile mycoflora. The rest of the isolated fungi also showed both cellulytic and proteolytic activities but to a lesser extent and with different capabilities for the two systems of enzymes. Therefore, the risk of textiles deterioration by their mycoflora is expected when the environmental conditions of the fabrics permit their growth.

Antimycotic Activity of Some Detergents

In order to prevent the biodeterioration of textiles and at the same time to avoid human health hazards, the mycoflora of textiles must be leached, before and during fabrics usages, two different detergents were tested. The results (Fig.

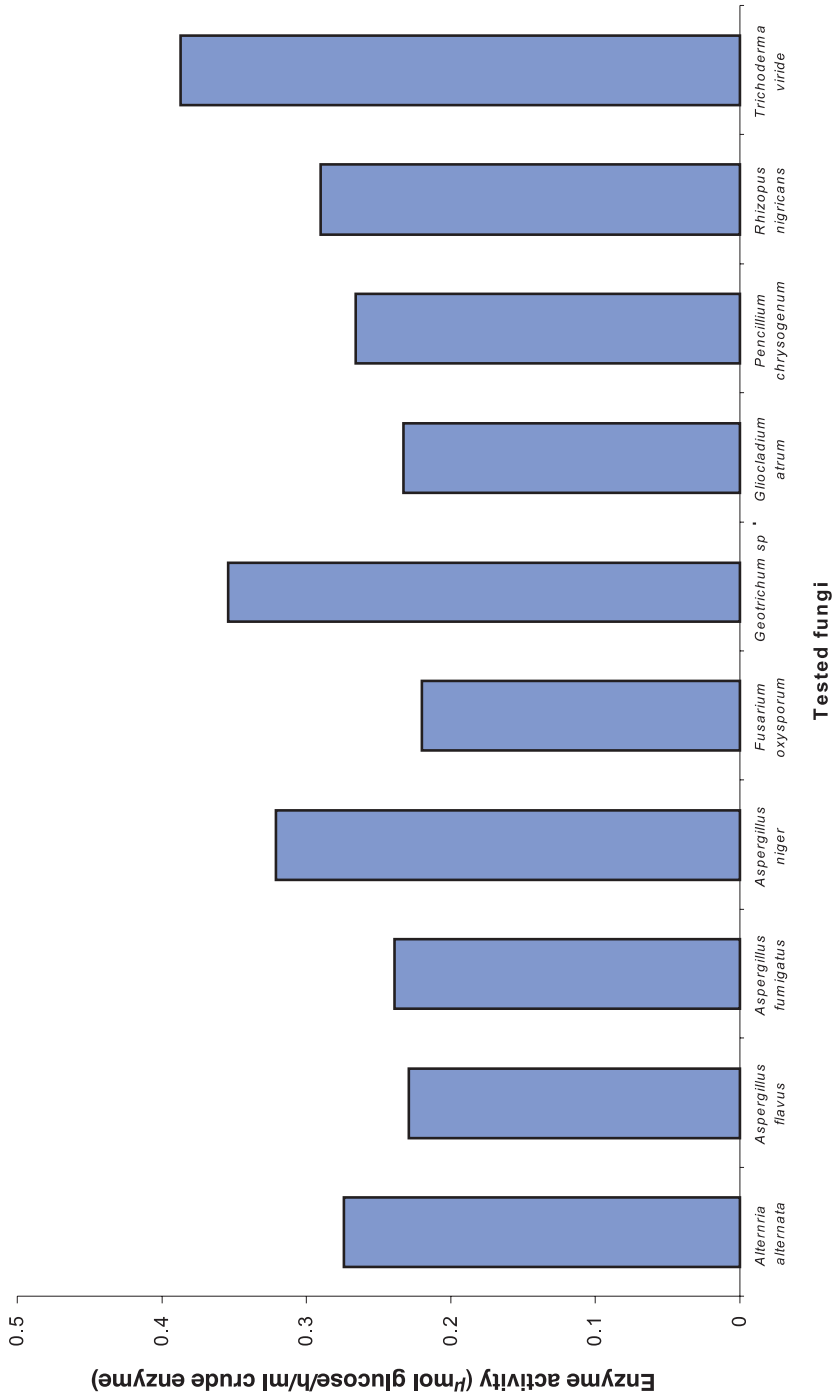


Fig. 4. Cellulytic activity of the tested fungi.

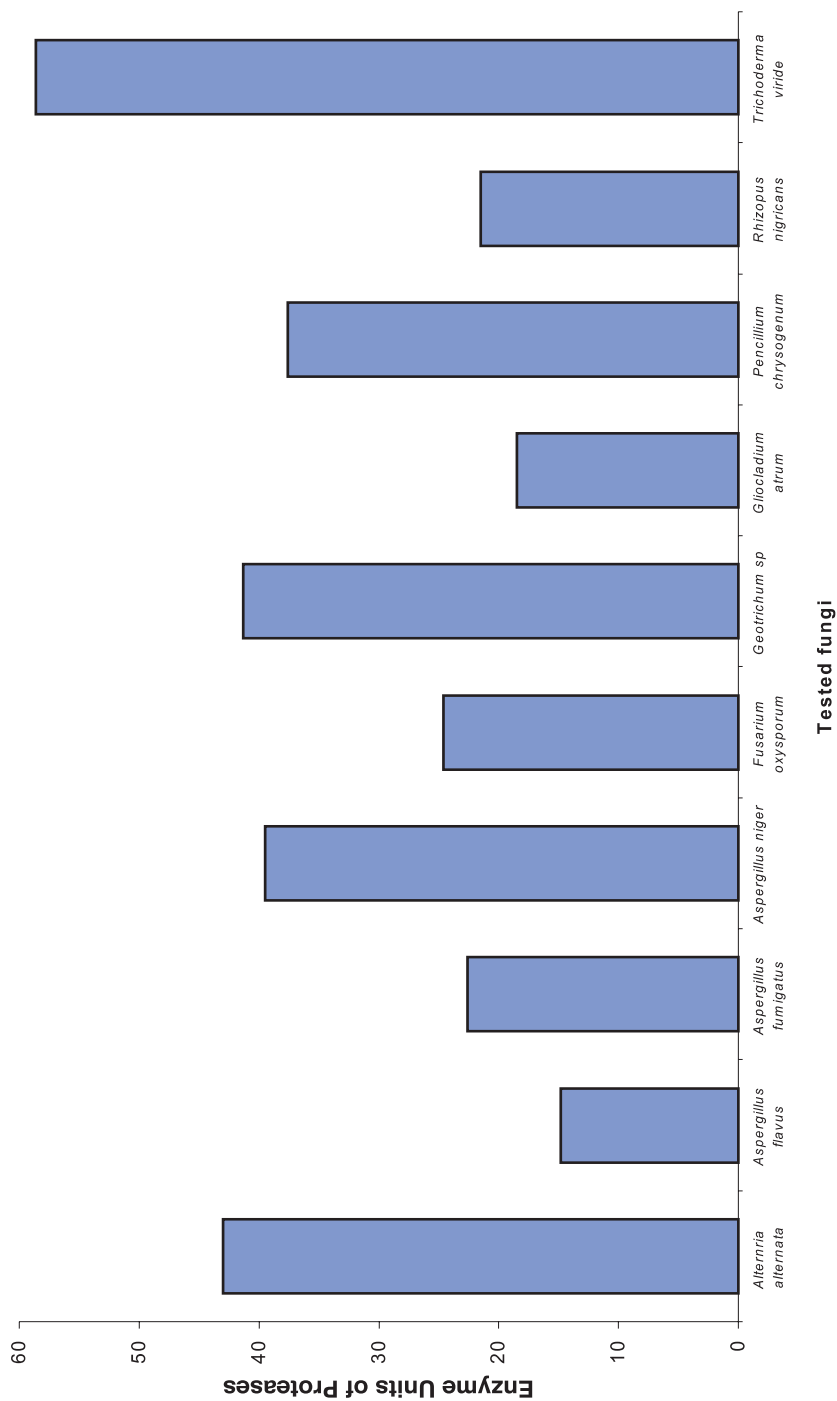


Fig. 5. Proteolytic activity of the tested fungi.

6) indicated that the tested fungi responded differently to the tested detergents, and their levels. *A. flavus* was the most sensitive fungus to Tide detergent and the same figure was recorded with *P. chrysogenum*, but under Ariel detergent treatment. On the other hand, the two detergents were conducive to inhibit the growth of *T. viride* especially at 16 g/l level. However, the increase of detergent level was concomitant with parallel inhibition to the fungal growth. *R. nigricans* was the least sensitive to the detergents treatments. The inhibitory effect of detergents may attribute to the toxic effect of some ingredients that elongate the fungal lag phase, inhibit normal cell elongation and spore germination. Detergents as surface active agents have detectable influences in permeability of the cell walls to different materials and metals [58,60-62].

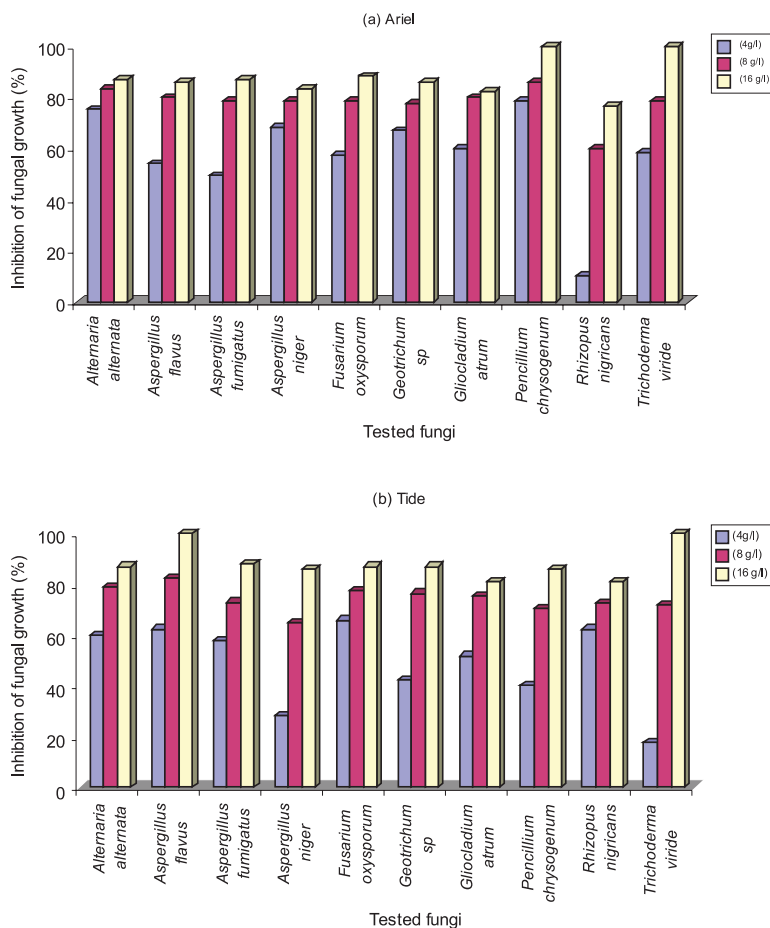


Fig. 6. Effect of two detergents (a - Ariel, b - Tide) at different concentrations on linear growth of the tested fungi.

References

- [1] **Haudek, H.W.** and **Viti, E.**, *Textilfasern*, Melli and Textilberichte K G, Heidelberg (1980).
- [2] **Raschle, P.**, Microbial influence on cellulosic textiles and microbiological testing, *J. International Biodeterioration*, **25** (3): 237-244 (1989).
- [3] **Wales, D.S.**, Synthetic fibres, finishing agents and their susceptibility to biodeterioration, *7th International Biodeterioration Symposium*, 6-11 Sept., Cambridge, UK (1987).
- [4] **Shimao, M.**, Biodegradation of plastics, *J. Current Technology*, **21** (1): 242-247 (2001).
- [5] **Tuffnell, P.**, The relationship of byssinosis of the bacteria and fungi in the air of textile mills, *Ibid.*, **17**: 307-309 (1960).
- [6] **Banerjee, U.C.**, **Weber, P.**, **Ruffin, J.** and **Banerjee, S.**, Airborne fungi survey of some residences in Durham North Carolina, U.S.A., *Grana*, **26**: 103-108 (1987).
- [7] **Dube, H.C.**, *Introduction of Fungi*, Vikas Publishing House Pvt Ltd., p: 608 (1990).
- [8] **Zyska, B.**, Fungi isolated from library materials – a literature review, *International Biodeterioration and Biodegradation*, **4** (1) : 43-51 (1997).
- [9] **Abdel-Hafez, S.I.I.**, **Mazen, M.B.** and **Barakat, A.**, Dust and airborne fungi in Egyptian cotton spinning factories, *The First International Conference on Basic Sciences and Advanced Technology*, Nov. 9-12, Assiut, Egypt (1996).
- [10] **Abdel-Hafez, S.I.I.**, **Mazen, M.B.** and **Barakat, A.**, Dust and airborne fungi of wool mills in Egypt, *Proceedings of the Second International Conference on Fungi: Hopes and Challenges*, 29 Sept. – 1 Oct., Cairo, Egypt, **II**: 13-28 (1999).
- [11] **Gupta, B.N.** and **Singh, K.P.**, Production and distribution of fungal spores and their medical significance, *Biol. Mem.*, **8**: 95-102 (1985).
- [12] **Tilak, S.T.**, Expanding horizons of aerobiology, *In Proceedings of III National Conference on Aerobiology* (ed. Chandra, N.), pp: 1-10, *Environmental Publications*, Karad. (1987).
- [13] **Tilak, S.T.**, *Air Borne Pollen and Fungal Spores*, Vivek Mudrandalaya, Aurangabad, India, pp: 125-130 (1989).
- [14] **Warden, J.** and **Highly, T.**, Survival and redeposition of fungi during laundering, *J. Home Economic Research.*, **1** (3): 2-13 (1974).
- [15] **Al- Gashgari, R.M.Q.**, A survey on the fungi associated with some fabrics in Jeddah (Saudi Arabia), *First Meeting in Home Economics*, King Abdulaziz University, Jeddah , Saudi Arabia (1999).
- [16] **Sharpe, A.N.** and **Jackson, A.K.**, Stomaching: A new concept in bacteriological sample preparation, *App. Microb.*, **24** (2): 175-178 (1972).
- [17] **Babb, J.R.**, **Davies, J.G.** and **Ayliffe, G.A.J.**, Contamination of protective clothing and nurses uniforms in an isolation ward, *J. Hosp. Infec.*, **4** (15): 149-157 (1983).
- [18] **Horborn, J.** and **Nystrom, B.**, Bacterial counts on fabrics: comparative study of three methods, *J. Hygenic London*, **95** (2): 403-407 (1985).
- [19] **McCarthy, B.J.**, **Senior, P.S.** and **Bakker, P.G.H.**, Microbiological testing of textile materials, *J. App. Bact. Society*, **33** (2): 39-49 (1987).
- [20] **Kease, M.**, **Meyer, G.**, **Schiden, R.** and **Wiedenboner, M.**, Specification system for mold on cotton fiber, *J. Mycology*, **13** (1): 402-411 (1997).
- [21] **Raper, B.K.**, **Thom, C.** and **Fennell, D. I.**, *A Manual of the Penicillia*, Hafner Publishing Company, London U.K. (1968).
- [22] **Gilman, J.**, *A Manual of Soil Fungi*, The Low State University Press, Ames Iowa, U.S.A. (1971).
- [23] **Barnett, H.L.** and **Hunter, B. B.**, *Illustrated Genera of Imperfect Fungi*, Burgess Publishing Company, New York (1972).

- [24] **Raper, B.K. and Fennell, D.I.**, *The Genus Aspergillus*, Robert E. Krieger, Publishing Company, Nalabar, Florida, U.S.A. (1977).
- [25] **Nelson, P.E., Toussour, A.T. and Cook, R.J.**, *Fusarium, Disease, Biology and Taxonomy*, Library of congress cataloging in publication data, U.S.A. (1981).
- [26] **Stevens, R.B.**, *Mycology Guide Book*, University of Washington Press, U.S.A. (1984).
- [27] **Moubasher, A.H.**, *Soil Fungi in Qatar and Other Arab Countries*, University of Qatar, Qatar (1993).
- [28] **Solomon, M.E.**, Control of humidity with potassium hydroxide, sulphuric acid, or other solutions, *Bulletin Eng. Res.*, **42** (3): 543-554 (1951).
- [29] **Mandels, M.**, Cellulose as a chemical and energy resource, *J. Biotech. Bioeng.*, **52** (5): 80-81 (1975).
- [30] **Miller, G.L.**, Use of dinitrosalicylic acid reagent for determination of reducing sugar, *J. Analytical Chem.*, **31** (3): 426-428 (1959).
- [31] **Safarik, I., Safarikova, E. and Miroslavo, A.**, Black substrate for spectrophotometric determination of cellulose activity in coloured solutions, *J. Bioch. Bioph. Methods*, **23** (2): 301-306 (1991).
- [32] **Plummer, D.T.**, *An Introduction to Practical Biochemistry*, McGraw-Hill, Bood Company, London, N.Y. (1987).
- [33] **Kunitz, M.**, Crystalline soybean trypsin inhibitor, II general properties, *J. General Physiology*, **30** (1): 291-310 (1946).
- [34] **Safarik, I.**, Spectrophotometric determination of proteolytic activity in coloured solutions, *J. Bioch. Bioph. Methods*, **19** (2): 201-206 (1989).
- [35] **Kavitha, N.S., Hilda, A., Gopinath, S. and Latha, K.**, Ecoethical technology using extracellular enzymes of *Chrysporium* sp. Bioethics in India, *Proceedings of the International Bioethics Workshop in Madars.*, *Biomangements of Biogeore Sources*, 16-19 Jan., University of Madars, India (1997).
- [36] **Marsh, P.B.**, Mildew and rot resistance of textiles, *J. Textile Res.*, **17** (3): 597-615(1974).
- [37] **Ayyangar, N.R.**, Mildew-resistant textiles, *J. Trade and Textile Industry*, **5** (33): 5-8 (1984).
- [38] **Lacey, J., Pepys, J. and Cross, T.**, Actinomycetes and fungus spore in air as respiratory allergan, In safety in microbiology, *Applied Bacteriology Board Society*, **6**: 151-184 (1972).
- [39] **Baur, X., Behr, J., Dewair, M., Ehert, W. and Zinkernagel, V.**, Humidifier lung and humidifier fever, *Lung.*, **166** (10): 113-124 (1988).
- [40] **Neely, A.N. and Orloff, M.M.**, Survival of some medically important fungi in hospital fabrics and plastics, *J. Clinical Microbiology*, **39** (9): 3360-336 (2001).
- [41] **Montegut, D., Indictor, N. and Koestler, R.J.**, Fungi deterioration of cellulosic textile, *J. Bioderiation and Biodegradation*, **28** (2) : 209-226 (1991).
- [42] **Yusef, H. and Allam, M.**, Studies on the physiology of certain fungi, I. Temperature relations, II. pH relations, *Bull. Faculty of Science, University of Alexandria*, Egypt, **7** (1): 137-162 (1965).
- [43] **Russell, B.S.**, *Mycological Guide Book*, Mycological Society of America, U.S.A. (1981).
- [44] **Maheshwari, R., Bharadwaj, G. and Bhat, M.K.**, Thermophilic fungi, their physiology and enzymes, *Microbiology and Molecular Biology Review*, **64** (3): 461-488 (2000).
- [45] **Griffin, D.H.**, *Fungal Physiology*, John Wiley and Sons, New York, Toronto (1981).
- [46] **Ramadani, A.S. and Aggab, A.M.**, Aldalophily among some filamentous fungi isolated from Saudi Arabia soils, *Arab Gulf J. Scientists Res.*, **11** (3): 403 -414 (1993).
- [47] **Mazan, M.B., Abdel-Hafaz, S.I., El-kady, I.A. and Maghraby, M.**, Effect of level of relative humidity on fungi and germination capacity of paddy (*Oryza sativa* L.) grains in Egypt, *Qatar Univ. Society J.*, **13** (1): 81-84 (1993).

- [48] **Block, S.S.**, Humidity requirement for mold growth, *J. Appl. Microbiol.*, **33** (1): 287-293 (1995).
- [49] **Betrabet, S.M., Usha, P.D. and Bhatt, I.G.**, Studies on cellulytic microorganisms. Part I: Microflora associated with degradation of cotton in storage in Bombay, *Textile Research J.*, **13** (30): 1189-1197 (1968).
- [50] **Abdel-Hafez, S.I.I.**, Cellulose decomposing fungi of desert soils in Saudi Arabia, *Mycopathologia*, **78** (1): 73-78 (1982).
- [51] **Sheir, H.M.**, Comparative studies on cellulytic activities of different isolates of *Rhizoctonia solani*, *J. King Saud University*, **15**(1): 63-69 (1984).
- [52] **Ahmad, J.S. and Baker, R.**, Competitive saprophytic ability and cellulytic activity of rhizosphere competent of *Trichoderma harzianum*, *Phytopathology*, **77** (2): 358-362 (1987).
- [53] **Galas, E. and Romanowska, I.**, Hydrolysis and transformation of cellulose with *Aspergillus niger* IBT-90, *Enz. Biotech.*, **17** (4): 339-349 (1997).
- [54] **Sanchez, J.G., Tsuchii, A. and Tokiwa, Y.**, Degradation of polycarpolactone at 50°C by a thermotolerant *Aspergillus* sp., *Biotechnology Letters*, **22**: 849-853 (2000).
- [55] **Balasubramanian, R. and Manocha, M.S.**, Proteinase, chitinase and chitosanase activities in germinating spores of *Piptecephalis virginiana*, *Mycologyia*, **72** (2): 157-168 (1986).
- [56] **Bagy, M.K. and Abdel-Mallek, A.Y.**, Fungi on the hair of small mammals in Egypt, *Cryptogamie Mycol.*, **12** (1): 63-69 (1991).
- [57] **Al-Sarrani, A.Q.**, Amylases, proteases and lipases production by *Monoascus rubber* Teigh., *Int. J. Exp. Botany*, **63** (1): 1-9 (1998).
- [58] **Al-Gashgari, R.M.Q. and Sadeak, A.A.N.**, Isolation of fungi from female hair samples collected in Jeddah, Saudi Arabia and the antifungal activity of various shampoos and soaps, *Bull. Pure and App. Sci.*, **18B** (2): 45-50 (1999).
- [59] **Moharram, A.M., Mohammed, A.I. and Alghalibi, S.M.**, Studies on mycotic keratitis in Assiut governorate, *Proceeding of the Second International Conference on Fungi: Hops and Challenges*, Cairo, 29 Sept. 1 – Oct., **3** (1): 133-146 (1999).
- [60] **Wiksell, J.C., Pickett, M.S. and Hartman, P.A.**, Survival of microorganisms in laundered polyester-cotton sheeting, *Appl. Microb.*, **25** (3): 431-435 (1973).
- [61] **Issa, A.A. and Ismail, M.A.**, Effect of detergents on River Nile water mycoflora, *J. Islamic Academy of Sciences*, **7** (3): 1-7 (1994).
- [62] **Ossowki, B., Duchmann, U. and Bolet, W.**, Disinfecting treatment of textiles to prevent reinfection in vulvovaginal candidiasis, *Geburtshilfe and Frauenheilkunde*, **59** (4): 175-179 (1999).

الفطريات المصاحبة لبعض المنسوجات في مدينة جدة

صالح محمد القرني، وصالح عبدالله كابلي، وفاطمة الشهري، وزكية القناوي

قسم علوم الأحياء، كلية العلوم، جامعة الملك عبد العزيز
ص.ب. ٨٠٢٠٣، جدة ٢١٥١٩ - المملكة العربية السعودية

المستخلص. تم عزل الفطريات المصاحبة لثمانية أنواع مختلفة من المنسوجات (ألياف طبيعية، وصناعية وخليط) جمعت من مراكز تسويقية في مدينة جدة بالمملكة العربية السعودية. وقد تم استخدام طرق التلامس، والتخفيف، والتجانس، والترطيب في عزل وتقدير أعداد وتعريف الفطريات المصاحبة للمنسوجات. وقد تم الحصول على ثلاث وعشرين عزلة فطرية، شكلت أنواع الأسبرجلس نسبة ٣٥٪ متبوعة بأنواع البنيسيليا والفيوزاريا بنسبة ١٣٪ لكل منهما. وقد سجلت أعلى أعداد الفطريات على منسوجات القطن (حتى عندما كانت مخلوطة) حيث بلغت ١٩٣٢ مستعمرة لكل سم^٢. جاءت بعدها منسوجات الصوف، بأعداد بلغت ١٤٢١ مستعمرة لكل سم^٢. وفي حين أظهرت منسوجات الحرير قابلية أقل للإصابة بالفطريات، كانت الأعداد الفطرية في منسوجات البوليستر متوسطة الكثافة.

كذلك تم اختبار تأثير بعض الظروف البيئية (مثل الحرارة والوسط الغذائي ودرجة الحموضة والرطوبة النسبية) على النمو الفطري لعشر من الفطريات المعزولة المعروفة بإحداث بعض الأضرار للإنسان وهي:

Alternaria alternata, *Aspergillus flavus*, *A. fumigatus*, *A. niger*, *Fusarium oxysporium*, *Geotrichum* sp., *Gliocladium atrum*, *Penicillium chrysogenum*, *Rhizopus nigricans*, *Trichoderma viride*.

ولقد أظهرت دراسة الأنشطة الإنزيمية للسليوليز والبروتييز تفوق *P. chry-* و *A. alternata* و *A. niger* و *Geotrichum* sp. و *T. viride* *sogenum*. كما أوضحنا دراسة النشاط التضادي لتوعين من المنظفات التباين في درجة التأثير على الفطريات المختبرة حسب نوع وتركيز المنظف.